

# JOURNAL OF THE STRUCTURAL DIVISION

## COMPARISON OF APPROXIMATE LINEAR METHODS FOR CONCRETE CREEP

By Zdeněk P. Bažant,<sup>1</sup> M. ASCE and Leonard J. Najjar<sup>2</sup>

### INTRODUCTION, METHOD OF APPROACH, AND SCOPE

The mathematical prediction of creep effects in concrete structures is a complicated task, even with the simplified linear forms of the creep law embodied in contemporary design recommendations (19,38). Engineers have, therefore, resorted to various approximate methods of analysis, such as the effective modulus method or the rate-of-creep method. The magnitude of the error which is due to the approximate nature of such methods has not been seriously studied, however, and intuitive judgment is widely relied upon to decide which of the various approximate methods should be used. The objective of this paper is to present the results of a detailed numerical study devoted to this question.

First it is necessary to decide on the criterion to be used for this purpose. Engineers tend to have most confidence in a direct comparison with measurements on structures. This viewpoint is undisputable when an empirical design formula for a very specific situation is under scrutiny; e.g., the camber of a composite beam of a certain cross-sectional type, certain dimensions, and reinforcement. However, generalization of such a formula to widely different cross-sectional types or dimensions, e.g., is usually unwarranted. Progress in design needs simple prediction methods of *general applicability*, and these can be achieved only through a rational theory which is based on the stress-strain law and structural mechanics. Two kinds of error in prediction of creep effects must then be discerned. One originates in the stress-strain law, and the other is due to the approximate nature of the method of analysis. Comparing the prediction directly

Note.—Discussion open until February 1, 1974. To extend the closing date one month, a written request must be filed with the Editor of Technical Publications, ASCE. This paper is part of the copyrighted Journal of the Structural Division, Proceedings of the American Society of Civil Engineers, Vol. 99, No. ST9, September, 1973. Manuscript was submitted for review for possible publication on March 14, 1973.

<sup>1</sup>Prof. of Civ. Engrg., Northwestern Univ., Evanston, Ill.

<sup>2</sup>Grad. Research Asst., Northwestern Univ., Evanston, Ill.

with measurements on structures, provides no way to separate the two kinds of error and, therefore, no information on the accuracy of the method as such is obtained. It is thus concluded that the judgment on the relative accuracy of the various methods of creep analysis in general should be made primarily on the basis of comparison with the mathematically exact solutions for the creep law adopted. This approach will be followed herein.

It should not be inferred, of course, that comparisons with the measurements on structures are of little value. But for interpretation of such comparisons it is necessary to know first the degree of accuracy of the method per se. For example, if the method is known to be accurate, and yet large discrepancy with the observations on structures is found, its source must be seen in inadequacy of the stress-strain law assumed.

It must be emphasized that in many cases accurate prediction of creep effects will require a nonlinear stress-strain law. Moreover, it will be necessary to consider that the strain depends not only on the stress history but also upon the histories of water content and temperature. At present, however, such a constitutive equation is in the stage of development (16).

In the past the question has been often examined (30,41) whether the best prediction of creep effects is achieved by using the superposition principle or by using the effective modulus, rate-of-creep, or rate-of-flow methods. In the writer's opinion, however, this question has been improperly posed. All of these methods are linear and thus they also obey the principle of superposition. But it is a superposition of certain distorted unit creep curves rather than the actual measured or given ones. In a specific case, of course, one of these methods may happen to compare with measurements better than superposition of the actual creep curves. Such a case arises especially in creep recovery after sudden complete unloading, and it is the rate-of-flow method (28) which was developed to fit this case. However, complete unloading is rare in practice, and small or gradual decreases of stress, as in relaxation type problems, agree with superposition of the actual creep curves as closely as can be discerned in presence of experimental scatter (see data fits in Figs. 10 and 20 of Ref. 18). Furthermore, it is not desirable to make the creep law fit the recovery after complete unloading because the prediction of the creep of old concrete is then inevitably sacrificed, as Fig. 1(a) will demonstrate. It should be remembered that any deviation from the principle of superposition is a *nonlinear* effect, so that efforts to correct the deviation by means of a linear creep law that corresponds to distorted unit creep curves (such as Eqs. 21 and 22 in the sequel) are a misconception. *Stopping short of a nonlinear creep law, nothing better than superposition is possible, in general.*

### LINEAR CREEP LAW OF AGING CONCRETE AND CONVERGENT NUMERICAL SOLUTION

A linear creep law is known to be acceptable for stresses less than about 0.4 of the strength, provided that large reversals of strain (not stress) and repeated loads are excluded and the variation of temperature and water content is not too severe. The linearity implies validity of the principle of superposition, which yields the uniaxial relation between stress  $\sigma$  and strain  $\epsilon$  as follows:

$$\epsilon(t) - \epsilon^0(t) = \int_0^t J(t, t') d\sigma(t') \quad (\text{Stieltjes integral}) \quad \dots \dots \dots (1)$$

in which  $t$  = observation time measured from casting of concrete;  $J(t, t')$  = creep function (or creep compliance) = strain at time  $t$  (including elastic strain) caused by a unit constant stress acting since time  $t'$ ; and  $\epsilon^0$  = stress-independent inelastic strain such as shrinkage or thermal dilatation. Eq. 1 for time-variable materials is due to Volterra (48) and was first applied to concrete by McHenry (36) and Maslov (35).

Creep is often characterized in terms of creep coefficient  $\phi(t, t')$  defined as:

$$\phi(t, t') = E(t') J(t, t') - 1 \quad \text{or} \quad J(t, t') = \frac{1 + \phi(t, t')}{E(t')} \quad \dots \dots \dots (2)$$

in which  $E(t') = 1/J(t', t')$  = instantaneous elastic modulus. According

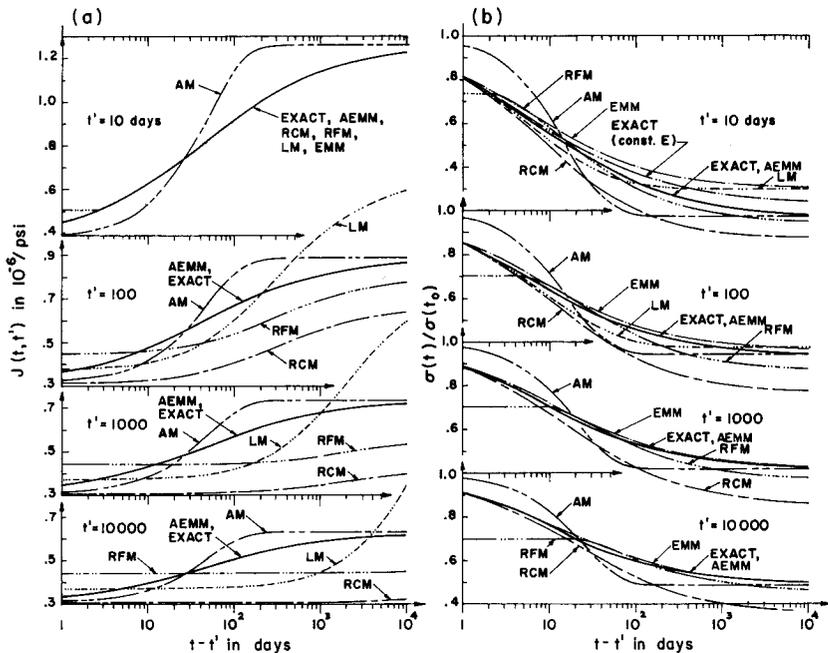


FIG. 1.—Comparisons of: (a) Simplified Forms of  $J(t, t')$  & (b) Predictions of Stress Relaxation [ $10^{-6}/\text{psi} = 145 \times 10^{-6}/(\text{N}/\text{mm}^2)$ ]

to the recent recommendation of an ACI subcommittee (19,20)

$$\phi(t, t') = \phi_u(t') f(t - t') \quad \dots \dots \dots (3)$$

$$\text{in which } f(t - t') = \frac{(t - t')^{0.6}}{10 + (t - t')^{0.6}} \quad \dots \dots \dots (4)$$

$$\phi_u(t') = \phi(\infty, 7) 1.25 t'^{-0.118} \quad \dots \dots \dots (5)$$

$$\text{and } E(t') = E(28) \sqrt{\frac{t}{4 + 0.85 t'}} \quad \dots \dots \dots (6)$$

$t, t'$  being given in days. Determination of  $\phi(\infty, 7)$  using a system of correction factors accounting for the effects of humidity, size, etc., is described in Ref. 19. Eq. 3, with a slightly different form of functions  $f$  and  $\phi_u$ , has been also adopted by CEB-FIP (see Refs. 38,44). For mass concrete, Eq. 4 is better replaced by  $f(t - t') = 0.113 \ln(1 + t - t')$ . More complicated expressions for  $J(t, t')$  which closely fit test data are given in Ref. 17.

Solution of structural analysis problems according to the creep law in Eq. 1 leads to Volterra's integral equations which can be solved only by numerical methods, of which the step-by-step methods are most efficient. For this purpose time  $t$  may be subdivided by discrete times  $t_0, t_1, t_2, \dots$  in time steps  $\Delta t_r = t_r - t_{r-1}$ . Time  $t_0$  coincides with the time of loading of the structure and if the loading is steady after time  $t_0$ , times  $t_0, t_1, \dots$  are best chosen in the form of a geometric progression (11) so that in  $\log(t - t_0)$ -scale  $\Delta t_r$  appears as constant. The integral in Eq. 1 may be approximated by the sum

$$\epsilon_r - \epsilon_r^0 = \sum_{q=1}^r \frac{1}{2} [J(t_r, t_q) + J(t_r, t_{q-1})] \Delta \sigma_q \quad \dots \dots \dots (7)$$

whose error is of the order of  $\Delta t^3$  (second-order method). Subscripts  $r, q$  refer to times  $t_r, t_q$  or to steps ending at these times, e.g.,  $\epsilon_r = \epsilon(t_r)$ , and  $\Delta \sigma_q = \sigma(t_q) - \sigma(t_{q-1})$ . Eq. 7 is applicable even when some time step, usually  $\Delta t_1$ , is of zero duration ( $t_1 = t_0$ ), i.e., the load increment is instantaneous. If  $r$  in Eq. 7 is replaced by  $r - 1$  and the equation thus obtained is subtracted from Eq. 7, the following relations may be verified:

$$\Delta \epsilon_r = \frac{\Delta \sigma_r}{E_r''} + \Delta \epsilon_r'' \quad \dots \dots \dots (8)$$

$$\text{in which } E_r'' = \frac{2}{J(t_r, t_r) + J(t_r, t_{r-1})} \quad \dots \dots \dots (9)$$

$$\Delta \epsilon_r'' = \sum_{q=1}^{r-1} \Delta \sigma_q \Delta J_{r,q} + \Delta \epsilon_r^0 \quad \text{for } r > 1; \quad \Delta \epsilon_r'' = \Delta \epsilon_r^0 \quad \text{for } r = 1 \quad \dots \dots (10)$$

$$\Delta J_{r,q} = \frac{1}{2} [J(t_r, t_q) + J(t_r, t_{q-1}) - J(t_{r-1}, t_q) - J(t_{r-1}, t_{q-1})] \quad \dots \dots \dots (11)$$

The error of the method is of the order of  $\Delta t^3$  (second-order method). To reduce the number of evaluations of creep function  $J$ , usually a costly part of the computations, expressions in Eqs. 9 and 11 may be replaced, without any loss in the order of error, by the expressions

$$E_r'' = \frac{1}{J(t_r, t_{r-(1/2)})};$$

$$\Delta J_{r,q} = J(t_r, t_{q-(1/2)}) - J(t_{r-1}, t_{q-(1/2)}); \quad (r > 2, q > 2) \quad \dots \dots \dots (12)$$

$$\text{in which } t_{q-(1/2)} = t_0 + \sqrt{(t_{q-(1/2)} - t_0)(t_q - t_0)} \quad \dots \dots \dots (13)$$

This is justified by the fact that under steady load stress  $\sigma$  varies within each time interval about linearly with  $\log(t - t_0)$ . Eq. 12 is obviously inapplicable

for the first two intervals beginning at  $t_0$  and at  $t_1 = t_0$  ( $r = 1, 2, q = 1, 2$ ). In all numerical studies reported in the sequel, the division  $t_r - t_0 = (t_{r-1} - t_0) 10^{0.1}$  has been used, which gave solutions that were exact to about 3 digits, as has been checked by varying the step size.

Eq. 8 has the form of an elastic stress-strain relation with elastic modulus  $E_r''$  and inelastic strain  $\Delta \epsilon''$ . Their values depend only on the stress increments prior to time step  $\Delta t_r$  and are thus known in advance, so that the solution of the increments  $\Delta \epsilon_r$  and  $\Delta \sigma_r$  during time step  $\Delta t_r$  is an elasticity problem. The only detail to be worked out is the determination of the effect of inelastic strains  $\Delta \epsilon_r''$  (see Appendix I).

Eqs. 8-11 were first used in Ref. 11, in which practical convergence of the method was studied. The first general formulation of the step-by-step integration seems to have been given in Ref. 8, using the form of creep law which arises from Eq. 1 on integration by parts. But for this form of the creep law, which has thus far prevailed in numerical studies, the long-term response cannot be computed with approximations of the type of Eq. 7 because it is impossible to increase the time step beyond a certain value (related to the shortest relaxation time) without causing numerical instability. Further refinements for nonlinear creep may be found in Ref. 12 and applications to redundant structures of composite cross section and to reinforced plates in Refs. 9 and 10. The rate-of-creep analysis of large structures as formulated in Refs. 4, 5, and 15 is a special case of the method used herein.

**APPROXIMATE METHODS OF ANALYSIS FOR LINEAR CREEP LAW**

In all approximate methods to be considered, the loads and enforced displacements are assumed to be steady or to vary at a rate decaying roughly as  $1/(t - t_0)$ ;  $t_0$  being the instant of introducing the first load or enforced deformation into the structure. Sudden load increments at various times  $t_0$  must be analyzed separately and the results then superimposed.

**Effective Modulus Method (EMM).**—This is the oldest, simplest, and most widespread method (37,29,30,38). It consists of a single elastic solution using the effective (or sustained) modulus  $E_{eff} = 1/J(t, t_0) = E(t_0)/[1 + \phi(t, t_0)]$ . This method is known to give excellent accuracy when the aging is negligible (43), as in old concrete. In such a case,  $J$  degenerates into a function of one variable ( $t - t'$ );  $\phi_u$  and  $E$  are constants; the creep curves ( $\epsilon$  versus  $t$ ) for loads applied at various ages  $t'$  are all identical and mutually horizontally translated; and all creep is incorrectly predicted as fully recoverable. Further, if  $J$  were, incorrectly, assumed to be bounded at  $t \rightarrow \infty$ , this method would give an exact solution for  $t \rightarrow \infty$  (42,43). In presence of aging, the creep due to stress changes after  $t_0$  is, obviously, overestimated.

**Age-Adjusted Effective Modulus Method (AEMM).**—Originated in 1967 by Trost (44), its rigorous and general formulation was first given in Ref. 14, on the basis of the following theorem (14).

**Theorem.**—If  $\epsilon(t) - \epsilon^0(t) = \epsilon_0 + \epsilon_1 \phi(t, t_0)$  for  $t \geq t_0$ , and  $\sigma = 0$  for  $t < t_0$ , in which  $\epsilon_0$  and  $\epsilon_1$  are arbitrary constants, then

$$\Delta \sigma(t) = E''(t, t_0) [\Delta \epsilon(t) - \Delta \epsilon''(t)] \dots \dots \dots (14)$$

in which  $\Delta \epsilon(t) = \epsilon(t) - \epsilon(t_0)$ ;  $\Delta \sigma(t) = \sigma(t) - \sigma(t_0) \dots \dots \dots (15)$

$$\Delta \epsilon''(t) = \frac{\sigma(t_0)}{E(t_0)} \phi(t, t_0) + \epsilon^0(t) - \epsilon^0(t_0) \dots \dots \dots (16)$$

$$E''(t, t_0) = \frac{E(t_0)}{1 + \chi(t, t_0) \phi(t, t_0)} \dots \dots \dots (17)$$

$$\chi(t, t_0) = \frac{1}{1 - \frac{E_R(t, t_0)}{E(t_0)}} - \frac{1}{\phi(t, t_0)} \dots \dots \dots (18)$$

in which  $E_R(t, t_0)$  = relaxation function = stress at time  $t$  due to constant unit strain imposed at time  $t_0$ . (The proof is given in Ref. 14.)

Because Eq. 14 has the form of Hooke's law, the computation of changes from  $t_0$  to  $t$  due to creep is reduced to a single elastic analysis with inelastic strains, as in EMM. The most important fact is that the values of  $\chi$  and  $E''$  are independent of  $\epsilon_0$  and  $\epsilon_1$  and are thus the same for any strain history which is linear with  $\phi(t, t_0)$ . Such histories closely approximate the strain variation in many practical situations. Coefficient  $\chi$  is called aging coefficient and  $E''$  age-adjusted effective modulus because  $\chi$  adjusts the effective modulus primarily for the aging effect; in absence of aging  $\chi \approx 1$  and  $E'' \approx E_{eff}$  (14). In the first studies (44,46,38,24) the term "relaxation coefficient" was used. This term was abandoned in Ref. 14 when it was found that  $\chi$  has nothing to do with stress relaxation and applies for time-increasing stress regimes as well. Tables and graphs of  $\chi$  for three basic forms of  $J(t, t')$  have been presented in Ref. 14, along with a simple computer algorithm for their accurate computation. When different nonproportional functions  $J(t, t')$  are used for different cross-sectional thicknesses, as is included in new CEB-FIP recommendations (21), this algorithm allows separate tables of  $\chi$  to be easily prepared for several typical thicknesses. Always  $\chi < 1$ , and usually, though not always,  $\chi > 0.5$ . It is noteworthy that a formula for stress relaxation which is equivalent to the extreme value  $\chi = 0.5$  was used by Hansen (31); the other extreme,  $\chi = 1$ , corresponds to EMM.

While EMM (as well as RCM, RFM, AM, LM in the following) gives an exact solution only when the stress is time-constant, this method gives an exact solution in infinitely many special cases, and especially three basic, diametrically different cases, i.e., the case of constant  $\sigma$  (as in the creep test), the case of constant  $\epsilon$  [as in the stress relaxation test (14)], and the case  $\epsilon = \epsilon_1 \phi(t, t_0)$ , typical of straining of structures by differential creep or shrinkage, and of buckling deflections. Because most other strain histories represent some kind of intermediate situation between the aforementioned cases, this method ought to be closer to the exact solution than the other approximate methods that coincide with the exact solution only in one special case (constant  $\sigma$ ).

**Rate-of-Creep Method (RCM).**—This method (in German called "Dischinger's method" and in Russian "theory of aging") is due to Glanville (30) and was first applied to more complicated problems by Dischinger (25,26). It admits simple solutions by assuming the creep law in the form of a first-order differential equation:

$$\frac{d\epsilon}{d\bar{\phi}} = \frac{1}{E(t)} \frac{d\sigma}{d\bar{\phi}} + \frac{\sigma}{E(t_0)} + \frac{d\epsilon^0}{d\bar{\phi}} \dots \dots \dots (19)$$

in which  $\bar{\phi}(t) = \phi(t, t_0)$ ;  $t_0$  being the instant the permanent load or enforced deformation is introduced into the structure. It can easily be shown (6,13,47) that Eq. 19 corresponds to an age-dependent Maxwell solid whose viscosity grows with age without bounds. Integrating Eq. 19

$$J(t, t') \approx \frac{1}{E(t')} + \frac{\bar{\phi}(t) - \bar{\phi}(t')}{E(t_0)} \dots \dots \dots (20)$$

in which  $\bar{\phi}$  is a function of one variable. To achieve further simplification of solutions,  $E$  is normally considered as constant. Eq. 20 is equivalent to Whitney's assumption (49) that the creep curves ( $\epsilon$  versus  $t$ ) for various  $t'$  are all identical but mutually vertically translated. Clearly, no delayed recovery is modeled; the creep due to stress changes after  $t_0$  is underestimated and a negligible creep is predicted for loads applied on very old concrete. But for loads applied on a very young concrete the method gives good results, in contrast with EMM. In relaxation type problems the prediction normally lies on the other side of the exact solution than that of EMM (6,13,47); but this is assured only in the case of monotonous time-dependence of all stresses.

**Rate-of-Flow Method (RFM).**—Prokopovich and Ulickii (p. 37 in Ref. 40) and independently (with a much more detailed justification) England and Illston (28,32,33) proposed to represent  $J(t, t')$  as a sum of delayed elastic component, which is recoverable, and flow, which is not. The flow corresponds to RCM, Eqs. 19 and 20, so that

$$J(t, t') \approx \frac{1}{E_d} + \frac{\phi_f(t) - \phi_f(t')}{E(t_0)}; \quad \frac{1}{E_d} = \frac{1}{E(t')} + \frac{\phi_d}{E(28)} \dots \dots \dots (21)$$

in which  $\phi_d$  and  $\phi_f$  denote creep coefficients for the delayed elastic strain and for the flow, respectively. Because the creep recovery curves at various ages are nearly identical,  $\phi_d$  depends only on  $(t - t')$  (28,40).

Thus, realizing that the effective modulus gives a very good approximation when aging is absent (14), Nielsen (39) proposed to treat the delayed elastic component in terms of the effective modulus,  $E_d$ , as defined in Eq. 21. Furthermore, for long range response, it is sufficient to take  $\phi_d$  as constant because the creep recovery curve reaches a final value relatively soon (28). Nielsen suggested  $\phi_d \approx 1/3$  and recently Rüsç and Jungwirth (21, 41 a) proposed  $\phi_d \approx 0.4$  (for  $t - t' > 90$  days). Consequently, to fit the measured or given creep curve  $J(t, t_0)$ , it must be assumed that:

$$\phi_f(t) = \phi(t, t_0) - \frac{\phi_d E(t_0)}{E(28)} \quad \text{or} \quad 0 \dots \dots \dots (22)$$

whichever is greater, in which  $\phi(t, t_0) = E(t_0) J(t, t_0) - 1$ . To date, only very simple problems, tractable by hand superposition of creep curves, have been solved with RFM. But the assumption of constant  $\phi_d$  makes the analytical solutions feasible, i.e., Eq. 21 is then formally equivalent to RCM and leads to the same differential equations and formulas in which effective modulus

$E_d$  for the delayed elastic component figures instead of  $E$ . [Rüsç and Jungwirth therefore speak of "improved Dischinger's method" (21,41 a).] The method is a hybrid of RCM and EMM. Accordingly, it should usually give solutions that lie between RCM and EMM, similarly as the exact solution.

**Levi's Method (LM).**—Levi (22,34) proposed the creep law to be assumed in the form:

$$\frac{d\epsilon}{d\bar{\phi}} + \frac{E_u}{E} \epsilon = \frac{1}{E} \frac{d\sigma}{d\bar{\phi}} + \frac{\sigma}{E} \dots \dots \dots (23)$$

which is modeled by a standard solid whose Maxwell unit has viscosity  $\eta = E_m / (d\bar{\phi} / dt)$  and elastic modulus  $E_m = E - E_u$ , and the parallel spring has modulus  $E_u$ ;  $\bar{\phi} = \bar{\phi}(t) =$  function of  $t$ . Integration yields:

$$J(t, t') = E^{-1} + (E_u^{-1} - E^{-1}) (1 - e^{-[\bar{\phi}(t) - \bar{\phi}(t')] E_u / E_m}) \dots \dots \dots (24)$$

Requiring that Eq. 24 fits exactly the measured or given  $\phi(t, t_0) = \bar{\phi}(t)$  it is found that  $\bar{\phi}(t) = -\ln [1 - \bar{\phi}(t) E_u / E_m] E_m / E_u$ , and from Eq. 24

$$J(t, t') = \frac{1}{E} + \left( \frac{1}{E_u} - \frac{1}{E} \right) \frac{\bar{\phi}(t) - \bar{\phi}(t')}{\frac{E}{E_u} - 1 - \bar{\phi}(t')} \dots \dots \dots (25)$$

while  $E_u$  may best be determined from the condition that Eq. 25 gives the correct value of  $J(2,000; 1,000)$ , as was assumed in the present study.

**Arutyunian's Method (AM).**—Arutyunian (2) proposed the approximation

$$J(t, t') \approx \frac{1}{E(t')} + \frac{\phi_u(t')}{E(t')} (1 - e^{-(t-t')/\tau_1}) \dots \dots \dots (26)$$

where for long-time creep effects a suitable choice is  $\tau_1 = 50$  days and  $\phi_u$  is the same as in Eq. 3. It can be shown to correspond to an age-dependent Kelvin model coupled in series with an age-dependent spring (13). It has the advantage that relaxation type problems can be reduced to first-order differential equations (with variable coefficients) for internal force rates or displacement rates (2), and a similar equation relates strain rates and stresses (13). In most problems with one unknown, analytical solutions are possible in terms of the incomplete gamma function, provided  $E =$  constant and  $\phi_u / E = A + B/t'$  or  $A + B e^{-t'/\tau_1}$  with  $A, B =$  constants is assumed (2,13). Applications of this method have flourished (2,7,13,23,27,40,47), especially in Eastern Europe, because, in contrast with EMM and RCM, the proper ratio between the creep of young aging and old non-aging concrete can be taken into account. But the exponential shape of creep curves is far from reality [Fig. 1 (17)] and the analysis is more complicated than for other methods.

Over the years, other more complicated and rarely used approximations have also been proposed to enable analytical solutions [e.g.,  $J(t, t')$  on p. 223 in Ref. 1 or a relaxation function similar to Eq. 26 (3,23)].

**COMPARISONS BETWEEN PREDICTIONS OF APPROXIMATE AND EXACT LINEAR METHODS**

Solutions for typical practical problems have been programmed in FORTRAN

IV using the method given by Eqs. 8-13. To spare programming effort, the solutions for RCM, RFM, LM, and AM have been obtained with the help of the same programs, replacing the subroutine that supplies the values of actual  $J(t, t')$  with a subroutine that supplies the values of  $J(t, t')$  according to the particular approximate method. The solutions for AEMM and EMM were also obtained with the same programs, using just one long step ( $t_0, t$ ), and  $\chi$  was

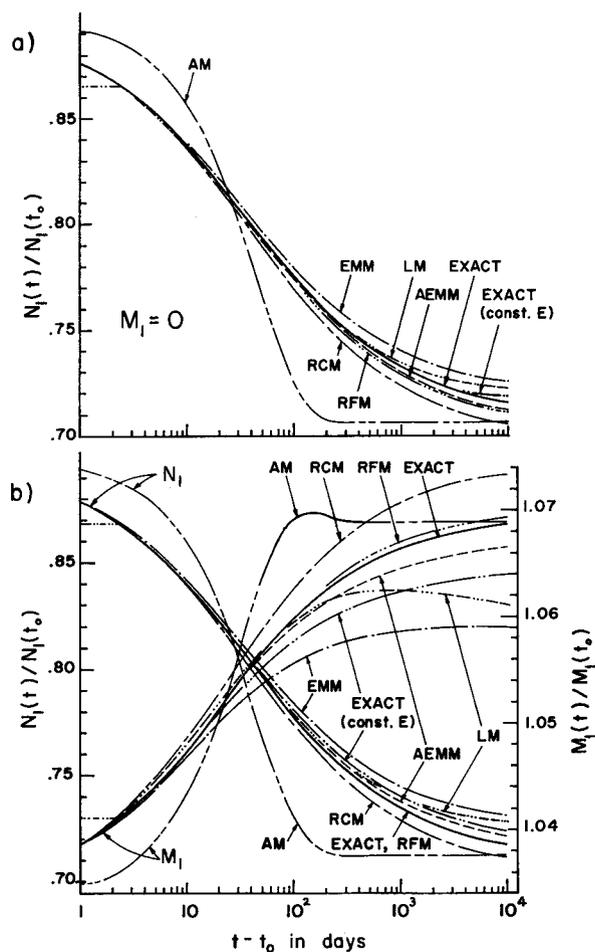


FIG. 2.—Development of Prestress Loss Due to Creep of Concrete (Including Elastic Loss)

determined by interpolation [linear in  $\log t'$  as well as in  $\log (t - t')$ ] from a table of  $\chi$ -values (14) computed in advance to four-digit accuracy. To assess the effect of variation of  $E$ , the exact solutions were also carried out for  $E(t) = E(t_0)$  constant. The results are presented herein (Figs. 1-6) only for creep properties given by Eqs. 2-6. Creep laws for RCM, RFM, and LM were always determined as to fit exactly  $\phi(t, t_0)$  for the  $t_0$ -value considered. In RFM,  $\phi_d$

$= 0.4$  was used. Predictions by AM are for  $\phi_u$  as given by Eq. 5. All curves are plotted in logarithmic time scale. (In the literature many arguments have been supported by comparisons in the actual time scale; but this is a misleading practice because only a certain narrow time range can be seen and the results

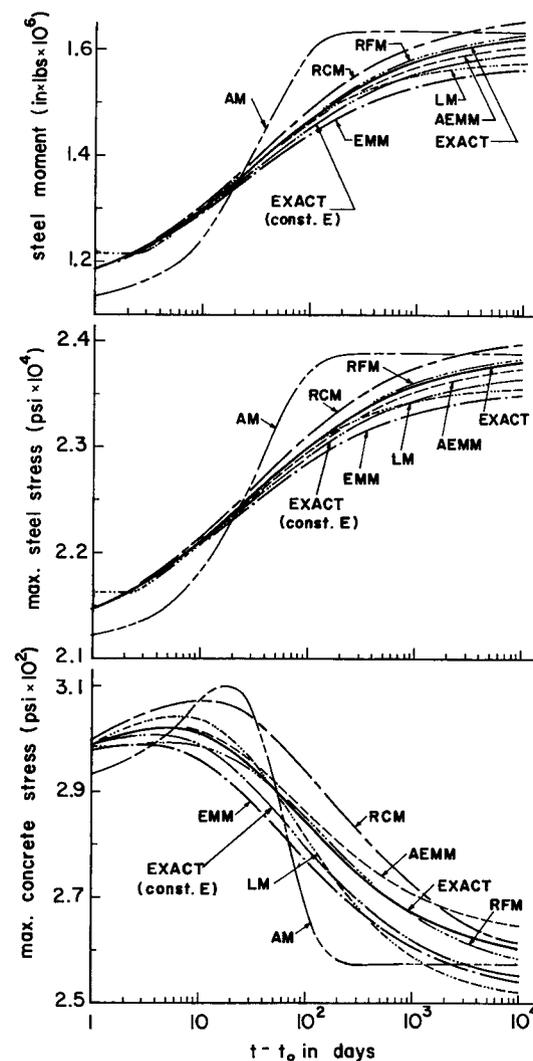


FIG. 3.—Changes of Stresses and Girder Moment Due to Creep in Steel-Concrete Composite Beam (100 psi = 0.6895 N/mm<sup>2</sup>; 10<sup>6</sup> in.  $\times$  lb = 112.5 kN  $\times$  m)

for both shorter and longer times are obscured.)

**Creep Function Approximation and Stress Relaxation.**—Fig. 1(a) compares the simplified forms of  $J(t, t')$ , as expressed by Eqs. 19 and 21, 22 and 24, and 25 and 26 with the given form: Eqs. 2-6 for  $E(28) = 3 \times 10^6$  psi (21,000

Mn/m<sup>2</sup>),  $\phi(\infty, 7) = 2.5$ . Note that creep deflections of most structures are roughly proportional to  $J(t, t')$ . The large error of RFM for high ages  $t'$  is inevitable if  $J(t, t_0)$  for all  $t$  is fitted exactly.

Fig. 1(b) compares the predictions of stress relaxation in terms of the ratio,  $\sigma(t)/\sigma(t_0)$ ;  $t_0$  being the time of imposition of constant strain;  $\phi(\infty, 7) = 2.5$ .

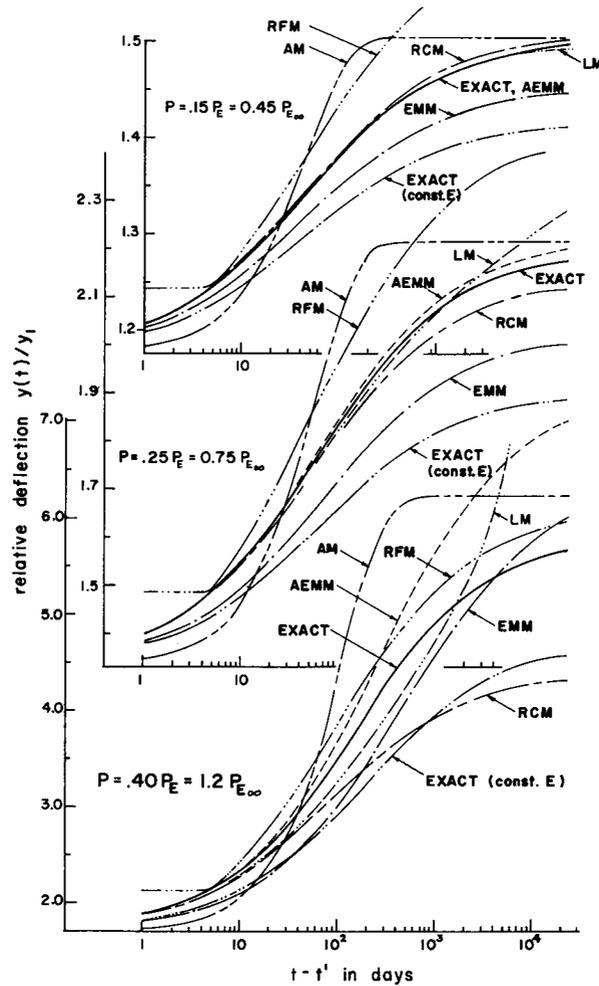


FIG. 4.—Creep Buckling Deflections of Slender Column Under Working Loads

(Creep law for both LM curves was taken for  $t_0 = 10$  days.) This case is characteristic of stress variation caused by enforced deformations in structures, such as differential settlements or deformations imposed by jacks for the purpose of decentering (of arches) or rectifying the state of the structure (as is often done in continuous beams or box girder bridges built by cantilevering). Variation of the forces in homogeneous structures after a change in statical system (e.g.,

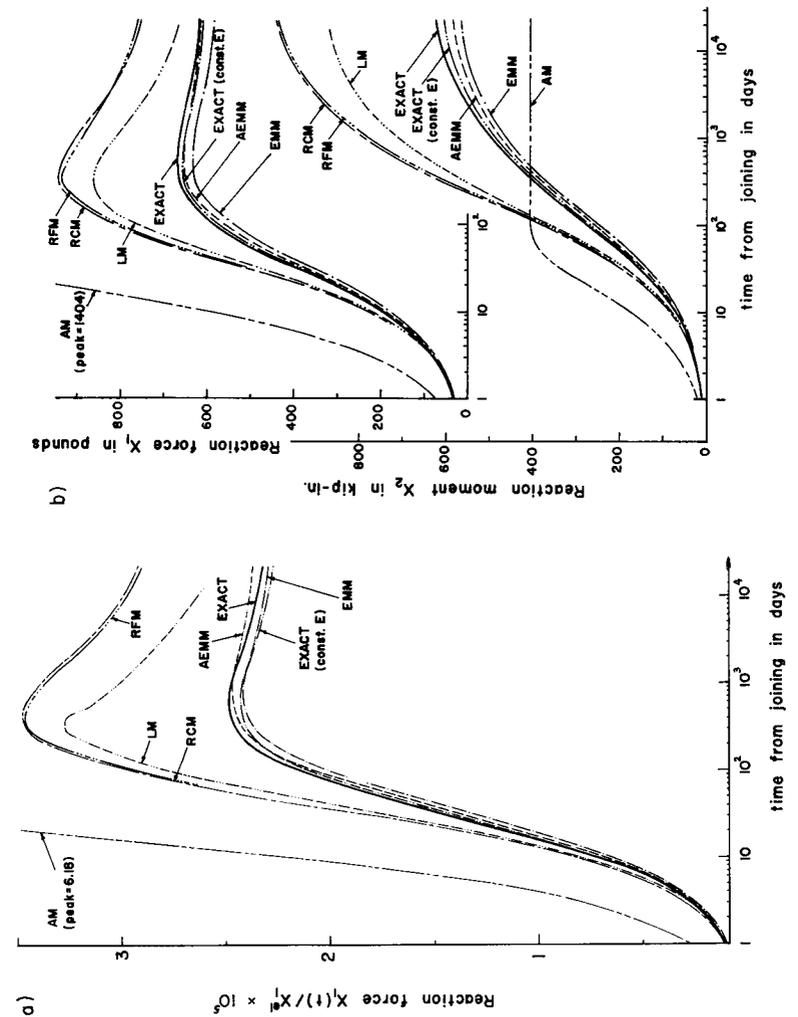


FIG. 5.—Forces in Midspan Connection of Two Cantilevers of Different Age, Due to Differential Creep (1 kip-in. = 112.5 N × m)

when a continuous beam is made by rigidly connecting simply supported beams) is also linearly related to stress relaxation function.

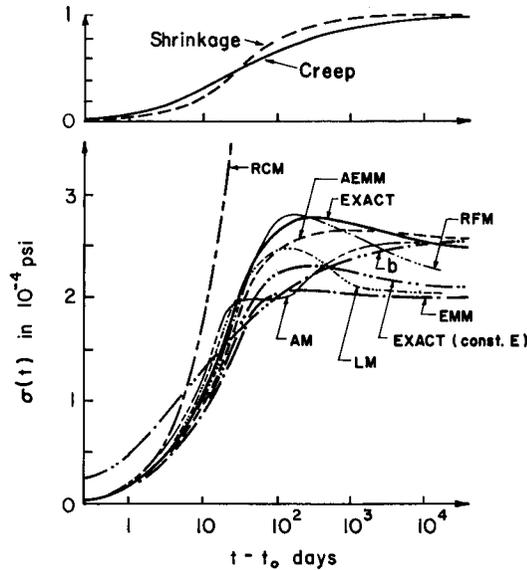


FIG. 6.—Shrinkage Stresses

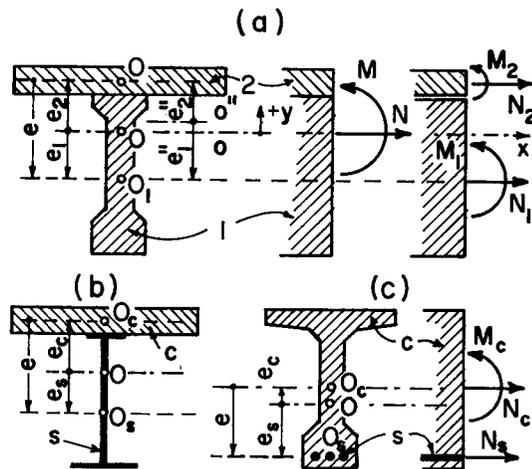


FIG. 7.—Cross Sections of Composite Beams

**Prestress Loss.**—Fig. 2 shows the development of prestress loss due to creep (including elastic loss) in a pretensioned statically determinate beam with a single layer of tendons (Fig. 7). In the notation defined in Appendix I and in Fig. 7,  $\phi(\infty, 7) = 2.35$ ;  $E_1 = 28.4 \times 10^6$  psi ( $196,000$  Mn/m<sup>2</sup>) (prestressing

steel);  $E_2 = E(28) = 5.68 \times 10^6$  psi ( $39,100$  Mn/m<sup>2</sup>) (concrete);  $I_1 \approx 0$ ;  $A_1 = 0.186$  in.<sup>2</sup> ( $1.195$  cm<sup>2</sup>);  $e = -3.50$  in. ( $-88.9$  mm);  $I_2 = 200$  in.<sup>4</sup> ( $8,300$  cm<sup>4</sup>);  $A_2 = 22.9$  in.<sup>2</sup> ( $147.4$  cm<sup>2</sup>);  $t_0 = 7$  days;  $M = N = 0$ ; and  $N_1(t_0) = 26,175$  lb; ( $116.2$  kN) = prestress before the elastic loss [while just after transfer  $N_1 = 23,450$  lb ( $104$  kN)]. Also included in Fig. 2 is the case of two layers of tendons (pretensioned): one on compression, one on tension side. The values of  $E_1, E_2, I_2, A_2, \phi(\infty, 7)$  were the same:  $I_1 = 2.437$  in.<sup>4</sup> ( $101.2$  cm<sup>4</sup>);  $A_1 = 0.248$  in.<sup>2</sup> ( $1.596$  cm<sup>2</sup>);  $e = -1.69$  in. ( $-42.9$  mm);  $M = N = 0$ ;  $N_1(t_0) = 29,220$  lb ( $130$  kN); and  $M_1(t_0) = 34,730$  lb  $\times$  in. ( $391$  kN  $\times$  cm) [while just after transfer  $M_1 = 29,340$  lb  $\times$  in. ( $330$  kN  $\times$  cm); and  $N_1 = 26,580$  lb ( $118$  kN)]. Noteworthy is the fact that differences between various methods are, in the case of prestress loss, unimportant and less than the unavoidable scatter of measurements. (Therefore, e.g., good comparison in Ref. 24 of AEMM predictions with test data should not have been regarded as a verification of AEMM.)

**Stress Redistributions and Deflections in Composite Beams.**—Fig. 3 gives the results for a statically determinate steel-concrete composite beam (Fig. 7). Shown are the predictions of stress  $\sigma_c$  in the top fiber of concrete stress  $\sigma_s$  in the bottom fiber of steel and bending moment  $M_1$  in the steel girder. Deflections are proportional to  $M_1$ . In the notation defined in Appendix I and in Fig. 7:  $E_1 = 30 \times 10^6$  psi ( $21,000$  Mn/m<sup>2</sup>) (steel girder);  $E(28) = E_2 = 2.52 \times 10^6$  psi ( $17,400$  Mn/m<sup>2</sup>) (concrete);  $I_1 = 800.0$  in.<sup>4</sup> ( $33,000$  cm<sup>4</sup>);  $A_1 = 14.71$  in.<sup>2</sup> ( $94.6$  cm<sup>2</sup>);  $e = -11.0$  in. ( $-279$  mm);  $I_2 = 341.3$  in.<sup>4</sup> ( $14,200$  cm<sup>4</sup>);  $A_2 = 256.0$  in.<sup>2</sup> ( $1,648$  cm<sup>2</sup>) and;  $N = 0, M = 2.52 \times 10^6$  lb  $\times$  in. ( $28,400$  MN/cm<sup>2</sup>). Value  $M$  was applied to the composite beam at  $t_0 = 7$  days of age of concrete.

**Creep Buckling Deflections.**—Fig. 4 presents the creep buckling deflections at midspan of a slender symmetrically reinforced square concrete column (Fig. 8) with small sinusoidal initial curvature. The results are given for axial loads from  $0.45 P_{E\infty}$  to  $1.2 P_{E\infty}$  in which  $P_{E\infty}$  = the long-time buckling load [stability limit (7,27); and  $P_{E\infty} = P_E / [1 + \phi(\infty, t_0)]$  which equals  $P_E / 3.00$  for  $\phi(\infty, 7) = 2.35$  and age at loading  $t_0 = 28$  days, as considered in this example. The column parameters, defined in Appendix I, are:  $L = 156$  in. ( $3,960$  mm) (Fig. 9);  $E_s = 30 \times 10^6$  psi ( $210,000$  MN/m<sup>2</sup>) (steel);  $E(28) = E_2 = 6 \times 10^6$  psi ( $41,000$  MN/m<sup>2</sup>) (concrete);  $I_s = 224.6$  in.<sup>4</sup> ( $9,340$  cm<sup>4</sup>); and  $I_c = 5,461$  in.<sup>4</sup> ( $227,000$  cm<sup>4</sup>).

It is seen that for axial loads exceeding the long-time buckling load the prediction of all approximate methods becomes poor. But this case is well beyond the range of working loads.

**Straining by Nonuniform Creep.**—Fig. 5 shows the development of the forces in the midspan connection of two cantilevers (Fig. 9) of different age, caused by differential creep. Each cantilever was assumed to be of uniform age and the left cantilever (part 1) was assumed to be 90 days older than the right one (part 2). (In Appendix I notation  $D_t^{(1)} = 0, D_t^{(2)} = 90$  days.) Joining was assumed to occur when the right cantilever was 90 days old ( $t_0 = 180$  days). The length of each cantilever was taken as  $L = 157.5$  ft ( $48$  m) and  $I$ -values at points spaced by  $L/8$  were assumed as  $7,438$  ft<sup>4</sup>,  $3,279$  ft<sup>4</sup>,  $1,263$  ft<sup>4</sup>,  $495$  ft<sup>4</sup>, and  $292$  ft<sup>4</sup> ( $64.2$  m<sup>4</sup>,  $28.3$  m<sup>4</sup>,  $10.9$  m<sup>4</sup>,  $10.9$  m<sup>4</sup>,  $4.27$  m<sup>4</sup>, and  $2.52$  m<sup>4</sup>). (These values were taken from the design of a bridge over Vltava at Hlandná in Czechoslovakia by one of the writers.) Furthermore  $E(28) = 4 \times 10^6$  psi

(28,000 MN/m<sup>2</sup>); and  $\phi(\infty, 7) = 2.5$ . A simplified load history was considered, assuming each cantilever to be loaded 60 days after casting by a constant

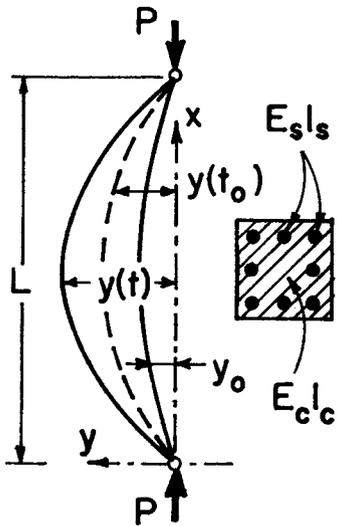


FIG. 8.—Creep Buckling of Reinforced Concrete Column

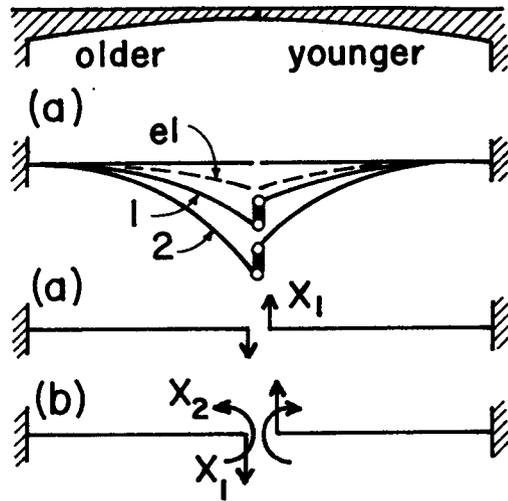


FIG. 9.—Two Cantilevers Joined at Midspan

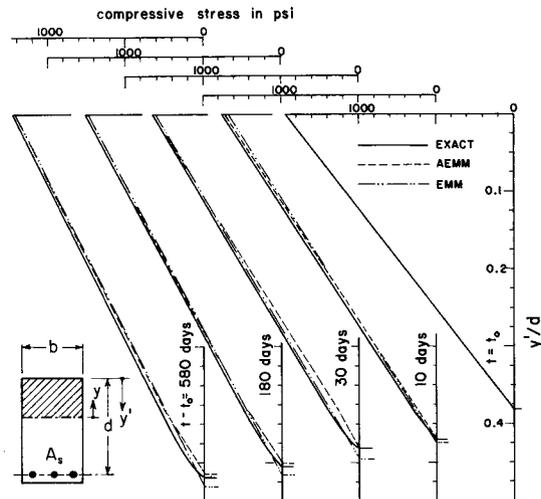


FIG. 10.—Effect of Creep on Stress Distributions in Cracked Reinforced Beam

distributed load of 10 lb/in. (1,700 N/m). Two cases were solved—cantilevers joined by a rigid hinged link [Figs. 5(a) and 9(a)] and joined monolithically [Figs. 5(b) and 9(b)]. The reactions in the connection immediately after joining were assumed as zero ( $X_1 = X_2 = 0$ ). Integrations along the cantilevers were

carried out by Simpson's rule. It should be noted that the RCM, RFM, and LM solutions were carried out exactly for creep given by Eqs. 20-22 and 25, while in the literature all RCM applications introduced a further simplification; the so-called affinity of  $\phi$ -curves for members of different age (see, e.g., Ref. 5), in order to facilitate analytical solutions. Value  $X_1^{el}$  = shear force at midspan due to a unit relative displacement of cantilever ends for  $E = E(28)$ . The exact solution for constant  $E$  is herein based on  $E(28)$  rather than  $E(t_0)$ .

**Shrinkage Stress.**—Fig. 6 shows the stresses induced by shrinkage when strain is kept zero. Shrinkage is assumed to begin at  $t_0 = 7$  days (beginning of drying exposure) and follow the curve  $\epsilon^0(t) = 0.0008(t - 7)/(35 + t - 7)$  (see Ref. 19). The exact and EMM, RCM, and AEMM solutions have already been given in Ref. 14 and herein the solutions for RFM, LM, and AM are added. The solution method is given in detail in Ref. 11. Note that AEMM would give exact solution (11) if the shape of the shrinkage curve was the same as that of the creep curve; keeping  $\epsilon^0(\infty)$  the same, this solution is shown as curve *b*. (Note that shrinkage induced forces in frames are proportional to the curves in Fig. 6.)

**Cracked Reinforced Beam.**—Fig. 10 reports the effect of creep upon the stress distribution in the rectangular cross section of a cracked singly reinforced concrete beam. The exact solution of this problem was obtained by Sackmann and Nickell (42). For material properties, see Ref. 42;  $b = 6.33$  in. (161 mm);  $d = 10$  in. (250 mm); and  $A_s = 1$  in.<sup>2</sup> (6.43 cm<sup>2</sup>) (Fig. 10).

## CONCLUSIONS

1. The proper criterion for evaluating general accuracy of the approximate methods based on a simplified linear creep function is a comparison with the exact solution according to the principle of superposition. The differences of the latter from the observed behavior of concrete can, in general, be formulated only in terms of a nonlinear creep law.

2. The age-adjusted effective modulus method (AEMM, Eqs. 14-18), along with the effective modulus method (EMM), is the simplest one because it reduces the creep problem to a single elastic analysis and, unlike the rate-of-creep (RCM), rate-of-flow (RFM), and other methods, it needs no differential equations to be solved. Also, in contrast with all other methods, it does not require any distortion of the experimentally observed or specified unit creep curves.

3. The AEMM is overall the most accurate method. It has been checked that this conclusion applies not only for the creep function in Eqs. 2-6, but also for other creep functions of the type suitable for concrete, as mentioned after Eq. 6.

4. The RFM along with the effective modulus treatment of the delayed elastic component (Eqs. 21 and 22) is, in general, about the second best one (the exception being recovery after sudden complete unloading, which RFM is made to fit). However, one has to resort to RFM in the case when a table of the aging coefficient required by AEMM is unavailable.

5. All curves (Figs. 1-6 and Fig. 10) for RFM, as well as RCM and AM, are for variable elastic modulus  $E$ , while in practice  $E$  is usually assumed, for the sake of simplicity, as constant. This, however, introduces into these methods an additional error whose magnitude is roughly the same as the deviation

of the exact solution curves for constant  $E$  from the exact solution curves for variable  $E$  (Figs. 1-6 and Fig. 10). But for variable  $E$  the solutions of the differential equations of RFM or RCM are unacceptably complicated for practical use.

6. The differences between various methods are significant in cases of stress relaxation, shrinkage stresses, creep buckling deflections, and straining of structures by differential creep, due to nonuniformity of concrete age. In the cases of prestress loss and stress redistributions in cracked reinforced concrete cross sections, the differences are unimportant and even the effective modulus method is sufficiently accurate in comparison with the statistical scatter observed in structural behavior.

7. Contrary to a widespread opinion, the effective modulus method and the rate-of-creep method do not always give opposite bounds on the exact solution, as Fig. 4 for creep buckling demonstrates.

8. Although the Arutyunian's method is mathematically most complicated, it is far from best. But its final values are much better than those of EMM or RCM.

9. Prediction of the complete time dependence is important since maximum stress may occur at a finite time (Figs. 3-6).

10. This study also shows that, in problems with a small number of unknowns, exact solutions for a linear creep law can be easily obtained.

On the basis of the present results, the age-adjusted effective modulus method has been proposed by the writers to be adopted by American Concrete Institute Committee 209 for its recommendations and the CEB (European Concrete Committee) Working Group for its manual for creep and shrinkage analysis currently under preparation.

**ACKNOWLEDGMENT**

The present research results have been obtained in connection with a project sponsored under the U.S. National Science Foundation Grant GK-26030.

**APPENDIX I.—DETAILS OF COMPUTATION OF CREEP EFFECTS**

**Composite or Prestressed Beams (Uncracked).**—Consider a general composite beam made of two parts, 1 and 2, each of which exhibits different linear creep properties. As a special case, one part may consist of steel, i.e., it has zero creep. Quantities referring to individual parts will be referred to by subscript  $i$  ( $i = 1, 2$ ). Denote  $N_1, N_2, M_1, M_2 =$  normal forces and bending moments in part 1 or 2 about its centroidal axis;  $A_1, A_2, I_1, I_2 =$  areas and moments of inertia of cross section of part 1 or 2 about its centroidal axis;  $e_1, e_2 =$  eccentricities of centroids  $O_1, O_2$  of Parts 1 and 2 from point  $O$  on the chosen beam axis- $x$ , positive when the vectors  $OO_1, OO_2$  point upwards, otherwise negative;  $e = e_1 - e_2 =$  distance between centroids of parts 1 and 2, positive when  $O_2O_1$  is oriented upwards, otherwise negative;  $N, M =$  normal force and bending moment about  $O$  in the whole cross section;  $k =$  curvature of beam;  $\epsilon_1, \epsilon_2, \epsilon_0 =$  normal strains in centroids  $O_1, O_2$ ; and point  $O$  on axis  $x$  (see Fig. 7).

The inelastic strain increments,  $\Delta\epsilon''_a, \Delta\epsilon''_b$ , are distributed linearly within each part and are equivalent to inelastic increments of curvature and strains in centroids, which are expressed, in analogy with Eqs. 10

$$\Delta k''_r = \sum_{q=1}^{r-1} \frac{\Delta M_{i,q} \Delta J_{i,r,q}}{I_i}; \quad \Delta \epsilon''_{i,r} = \sum_{q=1}^{r-1} \frac{\Delta N_{i,q} \Delta J_{i,r,q}}{A_i} \quad (i = 1, 2) \dots \dots \dots (27)$$

The equivalent inelastic bending moments and normal forces are

$$\Delta M''_i = E''_i I_i \Delta k''_i; \quad \Delta N''_i = E''_i A_i \Delta \epsilon''_i \quad (i = 1, 2) \dots \dots \dots (28)$$

in which  $E''_i =$  the values given by Eq. 9. The resultants over the whole cross section are

$$\Delta M'' = \Delta M''_1 + \Delta M''_2 - \Delta N''_1 e_1 - \Delta N''_2 e_2; \quad \Delta N'' = \Delta N''_1 + \Delta N''_2 \dots \dots (29)$$

Then, if the beam is statically determinate (otherwise see Ref. 9), the changes in curvature and axial strains during time interval  $\Delta t_r$  are

$$\left. \begin{aligned} \Delta k_r &= \frac{\Delta M_r + \Delta M'' - \sum_i (e''_i - e_i) (\Delta N + \Delta N'')}{R''_M} \\ \Delta \epsilon_{i,r} &= \frac{\Delta N_r + \Delta N''}{R''_N} - e''_i \Delta k \quad (i = 1, 2) \end{aligned} \right\} \dots \dots \dots (30)$$

in which

$$R''_N = \sum_i E''_i A_i; \quad e''_1 = \frac{e E''_2 A_2}{R''_N}; \quad e''_2 = e''_1 - e; \quad R''_M = \sum_i E''_i (I_i + A_i e''_i{}^2) \quad (31)$$

and  $\Delta M_r, \Delta N_r$  are given changes of  $M$  and  $N$  from time  $t_{r-1}$  to time  $t_r$  (zero in the cases studied herein). Finally, the changes of  $M_i, N_i$  during time interval  $\Delta t_r$  are

$$\Delta M_{i,r} = E''_i I_i \Delta k_r - \Delta M''_i; \quad \Delta N_{i,r} = E''_i A_i \Delta \epsilon_{i,r} - \Delta N''_i \quad (i = 1, 2) \dots \dots (32)$$

The foregoing procedure (Eqs. 27-32) is based on a general theorem given in Refs. 12, 16 or 41 where a more detailed description may be found. It was first applied in Ref. 5, in conjunction with the rate-of-creep method.

In the examples of prestress loss (Fig. 2) and the composite steel girder (Fig. 3) part 1 represented steel and was assumed with zero creep.

**Creep Buckling Deflections of Columns.**—Small deflections of a hinged slender symmetrically reinforced concrete column of length  $L$  has been studied (Fig. 8). The column is loaded by a constant axial force  $P$  (positive for compression) applied at time  $t_0$ . Assume that before loading,  $t < t_0$ , the column has a slightly curved shape,  $y_0 = a \sin (\pi x/L)$ ,  $x$  being the length coordinate. Denote  $E_s I_s, E_c I_c =$  bending rigidities of steel and concrete cross sections;  $k =$  curvature of column;  $M_c =$  bending moment carried by net concrete cross section; and  $y =$  deflection ordinate (measured from the chord). In analogy with Eqs. 8 and 10 for  $\Delta\epsilon''$ :

$$\Delta k_r = \frac{\Delta M_{c_r}}{E''_{c_r} I_c} + \Delta k''_c, \quad \Delta k''_c = \sum_{q=1}^{r-1} \Delta M_{c_q} \frac{\Delta J_{r,q}}{I_c} \dots \dots \dots (33)$$

in which  $E''_{c_r}$  is given by Eq. 9. Equilibrium of bending moment increments at constant  $P$  requires that:

$$\Delta M_{c_r} + E_s I_s \Delta k_r = -P \Delta y_r \quad (\Delta P = 0) \dots \dots \dots (34)$$

Eqs. 33 and 34 may be satisfied identically if both  $\Delta y_r$  and  $\Delta k$  have sinusoidal distributions, i.e.,  $y \sim \sin(\pi x/L)$ . Then  $\Delta k_r = d^2(\Delta y_r)/dx^2 = -\Delta y_r \pi^2/L^2$ , and substitution for  $\Delta k_r$  in Eqs. 33 and 34 furnishes:

$$\Delta y_r = \frac{E''_{c_r} I_c \Delta k''_c}{P - (E''_{c_r} I_c + E_s I_s) \frac{\pi^2}{L^2}}, \quad \Delta M_{c_r} = \left( E_s I_s \frac{\pi^2}{L^2} - P \right) \Delta y_r \dots \dots (35)$$

Computation in each time step proceeds through Eqs. 34 and 35 and values  $\Delta y_r$ ,  $\Delta M_{c_r}$  are evaluated only for the midspan. Note that values  $\Delta M_{c_r}$  from all previous time steps must be stored. The starting value due to initial elastic deflection at time  $t_0$  ( $r = 0$ ) is

$$\Delta M_{c_0} = \frac{P y_0}{P} \text{ in which } P_{E_0} = [E_c(t_0) I_c + E_s I_s] \frac{\pi^2}{L^2} \dots \dots \dots (36)$$

$$1 - \frac{P}{P_{E_0}}$$

The AEMM seems not to have yet been applied to creep buckling. Its formula is obtained as a single time step described in Eq. 35 and reads:

$$\frac{y(t)}{y(t_0)} = 1 + \frac{P}{P''_E - P} \frac{\phi(t, t_0)}{1 + \chi(t, t_0) \phi(t, t_0)} (1 - \rho_s) \dots \dots \dots (37)$$

$$\text{in which } \left. \begin{aligned} P''_E &= [E''_c(t, t_0) I_c + E_s I_s] \frac{\pi^2}{L^2} \\ \rho_s &= \frac{E_s I_s}{E_c(t) I_c + E_s I_s}, \quad y(t_0) = \frac{y_0}{1 - \frac{P}{P_{E_0}}} \end{aligned} \right\} \dots \dots \dots (38)$$

**Nonhomogeneous Structures of Nonuniform Age.**—Time  $t$  will now be viewed as a common reference age and  $t^{(p)}$  will denote the age of part  $p$  of the structure ( $p = 1, 2, \dots$ ). Let  $t^{(p)} = t - D_t^{(p)}$ , in which  $D_t^{(p)}$  = given age difference with respect to the chosen reference age.

Consider a statically indeterminate structure (e.g., Fig. 9) consisting of beams whose cross sections are, for the sake of simplicity, taken as homogeneous, with creep properties given by a certain creep function,  $J(t, t')$ . (For nonhomogeneous cross sections see Ref. 9.) Using a step-by-step analysis, the inelastic curvature increments during time step  $\Delta t$ , may be expressed, in analogy with Eq. 10:

$$\Delta k''_r = \sum_{q=1}^{r-1} \frac{\Delta M_q \Delta J_{r,q}^{(p)}}{I} \dots \dots \dots (39)$$

in which superscript  $p$  refers to part  $p$  and  $I$  = centroidal inertia moments of cross sections. Adopting the force method of analysis, the corresponding deformations of the primary system in the sense of the chosen redundants,  $X_i$  ( $i = 1, 2, \dots, N$ ), and the flexibility coefficients for time step  $\Delta t_r$ , are:

$$\Delta a_{i,r} = \int_{(x)} \bar{M}_i \Delta k''_r dx; \quad f''_{ij,r} = \int_{(x)} \frac{\bar{M}_i \bar{M}_j}{E''_r I} dx \dots \dots \dots (40)$$

in which  $x$  = length coordinate of beams;  $\bar{M}_i$  = bending moments due to state  $X_i = 0$ ,  $X_j = 0$  for all  $j \neq i$ ; and  $E''_r$  are the moduli given by Eq. 9 for the proper age of concrete in the cross section. Further, denote  $\Delta X_{i,q}$  = changes of redundants over time steps  $\Delta t_q$ , which must be stored for all steps; and  $\Delta M_q^L$  = changes of moments due to changes in given applied loads from time  $t_{q-1}$  to  $t_q$ . Substituting  $\Delta M_q = \Delta M_q^L + \sum_j \bar{M}_j \Delta X_{j,q}$  into Eq. 39 and Eq. 39 into Eq. 40, it can be found that

$$\Delta a_{i,r} = \sum_p \sum_{q=1}^{r-1} \left( \Delta a_{i,q}^{L(p)} + \sum_j f''_{ij,q} \Delta X_{j,q} \right) E_q^{(p)} \Delta J_{r,q}^{(p)} \dots \dots \dots (41)$$

$$\text{in which } \Delta a_{i,q}^{L(p)} = \int_{(x)} \frac{\bar{M}_i \Delta M_q^L}{E_q I} dx \dots \dots \dots (42)$$

Similarly, using Eq. 9

$$f''_{ij,r} = \sum_p f''_{ij,r}^{(p)} E_r^{(p)} J^{(p)}(t_r, t_{r-(1/2)}) \dots \dots \dots (43)$$

in which  $f''_{ij,r}^{(p)}$  and  $\Delta a_{i,q}^{L(p)}$  = the flexibilities and deformations due solely to part  $p$ . They are given by Eqs. 40 with modulus  $E(t_r^{(p)})$ , the integrals extending only over part  $p$ . The changes of redundants during step  $\Delta t_r$  are solved from the equations

$$\sum_j f''_{ij,r} \Delta X_{j,r} + \Delta a_{i,r} = 0 \dots \dots \dots (44)$$

In each time step the computation proceeds over Eqs. 42, 41, 43 and 44. The method is obviously also applicable even when  $J(t, t')$  is different for different cross sections.

**Cracked Reinforced Concrete Beam (Statically Determinate).**—The neutral axis is known to move, under permanent load, downwards, and the stress distribution between the original and the current position of neutral axis ( $y = 0$ ) becomes nonlinear. To describe this effect at least approximately, the distribution of stress below and above the current neutral axis has been assumed according to straight lines of different slopes. The stress distribution is then characterized by stresses  $\sigma_0$  at  $y = 0$  and  $\sigma_1$  at some chosen point  $y_1$ , and by the distance,

$c_n$ , from point  $y = 0$  to the final position of the neutral axis. Applying Eq. 14 of AEMM, the strain increments from time  $t_0$  to time  $t$  at points  $y = 0$  and  $y = y_1$  are

$$\Delta \epsilon_0 = \frac{\Delta \sigma_0}{E''}; \quad \Delta \epsilon_1 = \frac{\Delta \sigma_1}{E''} + \frac{\sigma_1(t_0)}{E(t_0)} \phi(t, t_0) \dots \dots \dots (45)$$

Further it is necessary to add one elastic relation for the stress increment in steel, two equations expressing that the strains in steel and in points  $y = c_n$ ,  $y = 0$ ,  $y = y_1$  must be linearly distributed, and finally two equations of equilibrium within the cross section. Thus seven algebraic equations for seven unknowns  $\Delta \epsilon_0$ ,  $\Delta \sigma_0$ ,  $\Delta \epsilon_1$ ,  $\Delta \sigma_1$ ,  $\Delta \epsilon_s$ ,  $\Delta \sigma_s$ ,  $c_n$  are obtained, which can be reduced to one cubic equation for  $c_n$ . The solution must be carried out in an iterative fashion. For the choice of point  $y = y_1$  various locations have been tried. It was found that for a rectangular cross section the best results are obtained when this point coincides with  $y = 0.8c$  (the case shown in Fig. 10), rather than the top fiber  $y = c$ .

#### APPENDIX II.—REFERENCES

- Aleksandrovskii, S. V., *Analysis of Plain and Reinforced Concrete Structures for Temperature and Moisture Effects, with Account of Creep* (in Russian), Stroyizdat, Moscow, U.S.S.R., 1966, p. 443.
- Arutyunian, N. K., *Some Problems in the Theory of Creep*, (in Russian), Tehteorizdat, Moscow, U.S.S.R., 1952. (English Translation, Pergamon Press, New York, N.Y., 1966; French Translation, Aroutiounian, Eyrolles, France, 1957).
- Babuška, I., and Mejzlík, L., "Calculation and Measurement of Thermal Stresses in Gravity Dams," 6th Congress of the International Commission on Large Dams, Vol. 2, New York, N.Y., 1958, pp. 483-513.
- Bažant, Z. P., "Approximate Methods of Analysis of Creep and Shrinkage of Complex Nonhomogeneous Structures and Use of Computers," (in Czech with English summary), *Stavebnický Časopis SAV*, Bratislava, Czechoslovakia, Vol. 12, 1964, pp. 414-431.
- Bažant, Z. P., Die Berechnung des Kriechens und Schwindens nicht-homogener Betonkonstruktionen, 7th Congress of the International Association for Bridge and Structural Engineering, held in Rio de Janeiro, Brazil, 1964, pp. 887-897.
- Bažant, Z. P., "Creep of Concrete in Structural Analysis," (in Czech), SNTL (State Publishing House of Technical Literature), Prague, Czechoslovakia, 1966, pp. 186.
- Bažant, Z. P., "Creep Stability and Buckling Strength of Concrete Columns," *Magazine of Concrete Research*, Vol. 20, 1968, pp. 85-94.
- Bažant, Z. P., "Linear Creep Problems Solved by a Succession of Generalized Thermoelasticity Problems," *Acta Technica ČSAV*, Prague, Czechoslovakia, Vol. 12, 1967, pp. 581-594.
- Bažant, Z. P., "Numerical Analysis of Creep of an Indeterminate Composite Beam," *Transactions*, American Society of Mechanical Engineers, Series E, *Journal of Applied Mechanics*, Vol. 37, 1970, pp. 1161-1164 (see also *ACI SP-27*, American Concrete Institute, 1971, pp. 373-385).
- Bažant, Z. P., "Numerical Analysis of Creep of Reinforced Plates," *Acta Technica Academiae Scientiarum Hungaricae*, Budapest, Hungary, Vol. 70, 1971, pp. 415-428.
- Bažant, Z. P., "Numerical Determination of Long-Range Stress History from Strain History in Concrete," *Materials and Structures*, Réunion Internationale des Laboratoires d'Essais et de Recherches sur les Matériaux et les Constructions, Vol. 5, 1972, pp. 135-141.
- Bažant, Z. P., "Numerical Solution of Non-Linear Creep Problems with Application to Plates," *International Journal of Solids and Structures*, Vol. 7, 1971, pp. 83-97.
- Bažant, Z. P., "Phenomenological Theories for Creep of Concrete Based on Rheological Models," *Acta Technica ČSAV*, Prague, Czechoslovakia, Vol. 11, 1966, pp. 82-109.
- Bažant, Z. P., "Prediction of Concrete Creep Effects Using Age-Adjusted Effective Modulus Method," *Journal of the American Concrete Institute*, Vol. 69, 1972, pp. 212-217.
- Bažant, Z. P., "Static-Structure Soil Interaction," *Revue Roumaine des Sciences Techniques, Serie de Mécanique Appliquée*, Vol. 17, 1972, pp. 1341-1361. (see also *Stavebnický Časopis SAV*, Vol. 12, 1964, pp. 542-558).
- Bažant, Z. P., "Theory of Creep and Shrinkage in Concrete Structures: A Précis of Recent Developments," *Mechanics Today*, American Academy of Mechanics, Pergamon Press, Vol. 2, 1973.
- Bažant, Z. P., and Wu, S. T., "Dirichlet Series Creep Function for Aging Concrete," *Journal of the Engineering Mechanics Division*, ASCE, Vol. 99, No. EM2, Proc. Paper 9645, Apr., 1973, pp. 367-387.
- Bažant, Z. P., and Wu, S. T., "Rate-Type Creep Law of Aging Concrete Based on Maxwell Chain," *Materials and Structures*, Paris, France, Vol. 7, No. 37, in press.
- Branson, D. E., et al., "Prediction of Creep, Shrinkage and Temperature Effects in Concrete Structures," Designing for Effects of Creep, Shrinkage and Temperature, Report of Committee 209, Subcommittee II, American Concrete Institute Special Publication No. 27, Detroit, Mich., 1971, pp. 51-93.
- Branson, D. E., and Christiason, M. L., "Time-Dependent Concrete Properties Related to Design," *Designing for Effects of Creep, Shrinkage and Temperature*, American Concrete Institute Special Publication No. 27, Detroit, Mich., 1971, pp. 257-278 (see also *Highway Research Record No. 324*, 1970 pp. 15-43, and 6th Congress International Federation for Prestressing, Prague, Czechoslovakia, June, 1970, pp. 22-52).
- Chiorino, M. A., Draft of CEB-FIP Manual on "Structural Effects of Time-Dependent Behavior of Concrete," Politecnico di Torino, Feb., 1972.
- Chiorino, M. A., and Levi, R., "Influence de l'Élasticité Différée sur le Régime des Contraintes des Constructions en Béton," *Cahiers de la Recherche No. 24*, Institut Technique du Batiment et des Travaux Publics, Eyrolles, Paris, France, 1967 (see also *Giornale del Genio Civile*, 1967; and *Accademia Nazionale dei Lincei*, fasc. 5, Series 8, Vol. 38, May, 1965).
- Courbon, J., "L'Influence du Fluage Linéaire sur l'Équilibre des Systèmes Hyperstatiques en Béton Précontraint," *Annales de l'Institut Technique du Batiment et des Travaux Publics*, Paris, France, No. 242, Feb., 1968.
- Dilger, W., and Neville, A. M., "Verification and Application of a New Method of Creep Analysis to Structural Members," *Preliminary Publication of the International Association for Bridge and Structural Engineering Symposium*, on "Design of Concrete Structures Creep, Shrinkage and Temperature Changes," held in Madrid, Spain, 1970, *IABSE Reports of the Working Commissions*, Vol. 5, 1970, pp. 253-260 (see also *ACI SP27*, American Concrete Institute, 1971, pp. 349-371).
- Dischinger, F., "Elastische und plastische Verformungen bei Eisenbetontragwerke," *Der Bauingenieur*, West Germany, Vol. 20, 1939, pp. 53-63, pp. 286-294, pp. 426-437.
- Dischinger, F., "Untersuchungen über die Knicksicherheit, die elastische Verformung und das Kriechen des Betons bei Bogenbrücken," *Der Bauingenieur*, West Germany, Vol. 18, 1937, pp. 487-520, pp. 539-552, pp. 595-621.
- Distéfano, J. N., "Creep Buckling of Slender Columns," *Journal of the Structural Division*, ASCE, Vol. 91, No. ST3, Proc. Paper 4369, June, 1965, pp. 127-150 (see also *Publication of International Association for Bridge and Structural Engineering*, Vol. 21, 1961, pp. 37-48).
- England, G. L., and Illston, J. M., "Methods of Computing Stress in Concrete from a History of Measured Strain," *Civil Engineering & Public Works Review*, 1965, pp. 513-517, pp. 692-694, pp. 846-847.
- Faber, O., "Plastic Yield, Shrinkage and other Problems of Concrete, and their Effect on Design," *Minutes of Proceedings of the Institution of Civil Engineers*, Vol. 225, London, England, (1927-1928), Nov., 1927, pp. 27-76, with discussions, pp. 75-130.
- Glanville, W. H., "Studies in Reinforced Concrete III—Creep or Flow of Concrete

- under Load," *Building Research Technical Paper No. 12*, Dept. of Scientific and Industrial Research, London, England, 1930 (see also: *Structural Engineer*, Vol. 11, 1933, p. 54; and *1st International Congress on Plain and Reinforced Concrete*, Liège, Belgium, 1930).
31. Hansen, T. C., "Estimating Stress Relaxation from Creep Data," *Materials Research and Standards (ASTM)*, American Society for Testing and Materials, Vol. 4, 1964, pp. 12-14.
  32. Illston, J. M., "Components of Creep in Maturing Concrete," *Journal of the American Concrete Institute*, Vol. 65, 1968, pp. 219-228.
  33. Illston, J. M., and Jordaan, I. J., "Creep Prediction for Concrete under Multiaxial Stress," *Journal of the American Concrete Institute*, Vol. 69, 1972, pp. 158-164.
  34. Levi, F., and Pizzetti, G., *Fluage, Plasticité, Précontrainte*, Dunod, Paris, France, 1951.
  35. Maslov, G. N., Thermal Stress State in Concrete Masses with Account of Concrete Creep (in Russian), *Izvestia Nauchno-Issledovatel'skogo Instituta VNII Gidrotekhniki (Gosenergoizdat)*, U.S.S.R., Vol. 28, 1940, pp. 175-188.
  36. McHenry, D., "A New Aspect of Creep in Concrete and its Application to Design," *Proceedings of the American Society for Testing Materials*, Vol. 43, 1943, pp. 1069-1086.
  37. McMillan, F. R., discussion of "Method of Designing Reinforced Concrete Slabs," by A. C. Janni, *Transactions, ASCE*, Vol. 80, 1916, p. 1738.
  38. Neville, A. M., and Dilger, W., Chaps. 17-20, *Creep of Concrete; Plain, Reinforced and Prestressed*, North Holland, Amsterdam, Netherlands, 1970.
  39. Nielsen, L. F., "Kriechen und Relaxation des Betons," *Beton-und Stahlbetonbau*, West Berlin, West Germany, Vol. 65, 1970, pp. 272-275.
  40. Prokopovich, I. E., *Effect of Long-Term Processes upon Stress and Strain States of Structures* (in Russian), Gosstroyizdat, Moscow, U.S.S.R., 1963, pp. 260.
  41. Ross, A. D., "Creep of Concrete under Variable Stress," *Journal of the American Concrete Institute*, Vol. 54, 1958, pp. 739-758.
  - 41a. Rüschi, H., Jungwirth, D., and Hilsdorf, H., "Kritische Sichtung der Verfahren zur Berücksichtigung der Einflüsse von Kriechen," *Beton- und Stahlbetonbau*, West Germany, Vol. 68, 1973, pp. 49-60, 76-86, 152-158.
  42. Sackman, J. L., and Nickell, R. E., "Creep of a Cracked Reinforced Beam," *Journal of the Structural Division*, ASCE, Vol. 94, No. ST1, Proc. Paper 5764, Jan., 1968, pp. 283-308.
  43. Schapery, R. A., "A Method of Viscoelastic Stress Analysis Using Elastic Solutions," *Journal of the Franklin Institute*, Vol. 279, 1965, pp. 268-289.
  44. Trost, H., "Auswirkungen des Superpositionsprinzips auf Kriech- und Relaxationsprobleme bei Beton und Spannbeton," *Beton-und Stahlbetonbau*, West Berlin, West Germany, Vol. 62, 1967, pp. 230-238, 261-269.
  45. Trost, H., and Mainz, B., "Zweckmäßige Ermittlung der Durchbiegung von Stahlbetonträgern," *Beton-und Stahlbetonbau*, West Berlin, West Germany, Vol. 64, 1969, pp. 142-146.
  46. Trost, H., and Wolff, H. J., "Zur wirklichkeitsnahen Ermittlung der Beanspruchungen in abschnittsweise hergestellten Spannbetontragwerken," *Der Bauingenieur*, West Germany, Vol. 45, May, 1970, pp. 155-179.
  47. Ulickii, I. I., Chan U. Y., and Bolyshev, A. V., *Analysis of Reinforced Concrete Structures with Respect to Long-Time Processes* (in Russian), Gosstroyizdat, Kiev, U.S.S.R., 1960, (495 pp.).
  48. Volterra, V., *Lecons sur les Fonctions de Ligne*, Gauthiers-Villars, Paris, France, 1913 (see also *Theory of Functionals and of Integral and Integro-Differential Equations*, Dover Publications, Inc., New York, N.Y., 1959).
  49. Whitney, G. S., "Plain and Reinforced Concrete Arches," *Journal of the American Concrete Institute*, Vol. 28, 1932, pp. 479-519; Discussion, Vol. 29, pp. 87-100.

### APPENDIX III.—NOTATION

The following symbols are used in this paper:

- $A_1, A_2, I_1, I_2, e_1, e_2, e_c, e_s, I_c, I_s, e_c, e_s$  = areas, inertia moments, and eccentricities of parts of composite cross section (Fig. 7, Appendix I);
- $a_i, f_{ij}$  = deformations due to loading and flexibility coefficients (Eqs. 40, 45);
- $D_i^{(p)}$  = reference age minus age of part  $p$  (at same instant);
- $E''$  or  $E''_r$  = pseudo-instantaneous modulus (Eq. 11a) or age-adjusted effective modulus (Eq. 14);
- $E_c, E_s$  = moduli of concrete and of steel in composite structure;
- $E_u, E_m$  = moduli in Eqs. 23, 24;
- $E(t) = 1/J(t, t)$  = elastic modulus of concrete in time  $t$ ;
- $f(t - t')$  = function of  $t - t'$  in Eq. 3;
- $J(t, t')$  = creep function (or creep compliance) defined after Eq. 1;
- $k, \Delta k''$  = curvature of beam and its inelastic increment;
- $M, N, M_1, N_1, M_2, N_2, M_c, N_c, M_s, N_s$  = bending moment and normal force in cross section and in its Parts 1 and 2 or concrete and steel parts (Fig. 7, Appendix I);
- $\bar{M}_i$  =  $M$  in primary system due to  $X_i = 1$ ;
- $P_E, P_{E_x}$  = instantaneous and long-time buckling load (stability limit) of column;
- $t, t'$  = time from casting of concrete, in days;
- $t = t'$  = time elapsed from loading;
- $t_0$  = instant of introducing first load or enforced deformation into structure;
- $t_r, t_q, t_{q-1/2}$  = chosen discrete times for step-by-step analysis ( $r, q = 1, 2, 3, \dots$ ), and time given by Eq. 9;
- $X_i$  = statically indeterminate quantities;
- $y$  = column deflection (at midspan in Fig. 4) or depth coordinate in cross sections;
- $\Delta$  = increment sign for interval  $t_{r-1}, t_r$ ; e.g.,  $\Delta \epsilon_r = \epsilon_r - \epsilon_{r-1}$ ;
- $\Delta J_{r,s}$  = expression defined by Eq. 12;
- $\Delta \epsilon''$  = pseudo-inelastic strain increment in Eq. 11b or Eq. 14;
- $\epsilon, \epsilon^0$  = total strain and stress-independent inelastic strain (shrinkage, e.g.);
- $\phi(t, t')$  = creep coefficient (Eq. 2); and
- $\phi_f, \phi_u, \bar{\phi}, \bar{\phi}$  = coefficients defined by Eqs. 21, 3, 19, 23.

### Subscripts

- $c, s$  = for concrete and steel;
- $i$  = 1, 2 for parts 1 and 2 or composite section (Fig. 7); and
- $r, q$  = for discrete times  $r, q$ ,  $\epsilon_r = \epsilon(t_r)$ ,  $J_{r,q} = J(t_r, t_q)$ , etc.

### Superscript

- ( $p$ ) = for part  $p$  of structure (Appendix I).

## 10006 APPROXIMATE LINEAR METHOD FOR CONCRETE CREEP

**KEY WORDS:** Aging tests (materials); Approximation method; Beams (supports); Bridges (structures); Composite beams; **Concrete**; **Concrete (prestressed)**; Concrete (reinforced); **Creep**; Creep rate; Deflection; Design practices; Numerical analysis; Predictions; Shrinkage; Stresses; **Structural engineering**

**ABSTRACT:** The approximate methods for prediction of structural effects of creep, such as the effective modulus (EMM), age-adjusted effective modulus (AEMM), rate-of-creep (RCM), rate-of-flow (RFM), and Levi's and Arutyunian's Methods are all linear and satisfy the principle of superposition. Predictions of the approximate methods are compared with the "exact" numerical solutions based on the principle of superposition and given (undistorted) realistic unit creep curves. It is found that AEMM is in general superior to all other methods and along with EMM is also the simplest one RFM (with effective modulus treatment of delayed elastic strain) appears as second best and should be resorted to when the table of aging coefficient required by AEMM is unavailable.

**REFERENCE:** Bazant, Zdenek P., and Najjar, Leonard J., "Comparison of Approximate Linear Methods for Concrete Creep," *Journal of the Structural Division*, ASCE, Vol. 99, No. ST9, **Proc. Paper 10006**, September, 1973, pp. 1851-1874